

**RADIOGRAPHIC EXAMINATION REPORT**

<b>Customer</b> : MICROFUSION CAST & ALLOYS, METODA	<b>Report No.</b> : 27881/25-26
<b>Customer's Client</b> :	<b>Date</b> : 26/03/2026
<b>Job Description</b> : 2" (DN50) FIG-630 BODY #300	<b>Date of Test</b> : 21/03/2026
<b>Die / Tool No.</b> : 1211 <b>Drg. No.</b> :	<b>Offer No.</b> : 2020
<b>Heat No.</b> : E665 <b>PO No.</b> :	<b>WAS No.</b> :
<b>Material</b> : WCB	<b>Test Carried Out At</b> : OUR TEST LAB
<b>Procedure Followed</b> : ASME Sec V,Arti-2 & 22,2025	<b>RT Coverage</b> : B16.34
<b>Evaluation Standard</b> : ASTM E-446 (Vol II),2020	<b>Procedure No.</b> : PS05/I6 REV.5
<b>Acceptance Standard</b> : ASME B16.34 APPENDIX-1 2025	<b>Shooting Sketch No.</b> :

<b>Radiation Source</b> : Ir-192	<b>Screen</b> : LEAD 0.10mm Front , 0.10mm Back	<b>Film Processing</b> : MANUAL
<b>Source Strength</b> : 17.98 Ci	<b>Exposure Time</b> : VARIOUS MIN	<b>Processing Time</b> : MANUAL
<b>Source Size</b> : 2.7mmD x 1.2mmH	<b>Film Brand &amp; Type</b> : FILM D7	

Sr. No.	Identification	Location	Film Size (inch)	Techq.	Thck. (mm)	Density	SFD (inch)	IQI	Sensitivity	Findings	Result
1	RT 1555	A	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	CB - III	Acceptable
2	RT 1555	B	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	CB - III	Acceptable
3	RT 1555	C	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	CB - II	Acceptable
4	RT 1555	PA-B	4X6	SWSI	38	2.0 TO 4.0	4	ASTM 1B	S W10	B - I	Acceptable

**Total No. of Films** : 4 Nos., **Total Sq. Inches** : 168.00  
**Film Size Summary** : 6X8 - 3, 4X6 - 1

Density of each film is measured and confirm between 2.0 TO 4.0  
NSD=No Significant Discontinuity, A=Gas Porosity, B=Inclusion, CA;CB;CC;CD=Shrinkage, D=Crack, E=Hot Tears, F=Insert, SD=Surface Depression, G=Mottling

**Note :**  
1. Report relates items tested only.  
2. Test Results are in compliance with requirements and / or specifications of technique used.  
3. Test Reports shall not be reproduced except full in written approval of the Laboratory.

<b>For, Capital NDT Services</b>	<b>Customer Representative</b>	<b>Customer's Client</b> :	<b>Inspection Agency</b> :
<p>KAUSHIK USDAO ASNT RT-II</p>	<p>ASNT Level-II LP, MP, UT, RT, VT CHINTAN K. NAYTHIYA</p>		



# CAPITAL NDT SERVICES

Survey No. 72, Paikee 1 / Paikee 2 / Paikee 2, Plot No. 5, Dev Industrial Area, Village Bhunava, Tal Gondal, Dist. Rajkot (Gujarat, India)  
Phone : +91 95861 23523, +91 95862 23523, Email : capitalndts@gmail.com



## RADIOGRAPHIC EXAMINATION REPORT

<b>Customer</b> : MICROFUSION CAST & ALLOYS, METODA	<b>Report No.</b> : 27882/25-26
<b>Customer's Client</b> :	<b>Date</b> : 26/03/2026
<b>Job Description</b> : 2" (DN50) FIG-630 BODY #300	<b>Date of Test</b> : 21/03/2026
<b>Die / Tool No.</b> : 1211 <b>Drg. No.</b> :	<b>Offer No.</b> : 2020
<b>Heat No.</b> : E665 <b>PO No.</b> :	<b>WAS No.</b> :
<b>Material</b> : WCB	<b>Test Carried Out At</b> : OUR TEST LAB

<b>Procedure Followed</b> : ASME Sec V,Art-2 & 22,2025	<b>RT Coverage</b> : B16.34
<b>Evaluation Standard</b> : ASTM E-446 (Vol II),2020	<b>Procedure No.</b> : PS05/I6 REV.5
<b>Acceptance Standard</b> : ASME B16.34 APPENDIX-1 2025	<b>Shooting Sketch No.</b> :

<b>Radiation Source</b> : Ir-192	<b>Screen</b> : LEAD 0.10mm Front , 0.10mm Back	<b>Film Processing</b> : MANUAL
<b>Source Strength</b> : 17.98 Ci	<b>Exposure Time</b> : VARIOUS MIN	<b>Processing Time</b> : MANUAL
<b>Source Size</b> : 2.7mmD x 1.2mmH	<b>Film Brand &amp; Type</b> : FILM D7	

Sr. No.	Identifi- cation	Location	Film Size (inch)	Techq.	Thck. (mm)	Density	SFD (inch)	IQI		Sensi tivity	Findings	Result
1	RT 1556	A	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S	4T	B/CB - I/I	Acceptable
2	RT 1556	B	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S	4T	B - I	Acceptable
3	RT 1556	C	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S	4T	B - I	Acceptable
4	RT 1556	PA-B	4X6	SWSI	38	2.0 TO 4.0	4	ASTM 1B	S	W10	NSD	Acceptable

**Total No. of Films** : 4 Nos., **Total Sq. Inches** : 168.00  
**Film Size Summary** : 6X8 - 3, 4X6 - 1

Density of each film is measured and confirm between 2.0 TO 4.0  
NSD=No Significant Discontinuity, A=Gas Porosity, B=Inclusion, CA,CB,CC;CD=Shrinkage,  
D=Crack, E=Hot Tears, F=Insert, SD=Surface Depression, G=Mottling

**Note :**  
1. Report relates items tested only.  
2. Test Results are in compliance with requirements and / or specifications of technique used.  
3. Test Reports shall not be reproduced except full in written approval of the Laboratory.

<b>For, Capital NDT Services</b>	<b>Customer Representative :</b>	<b>Customer's Client :</b>	<b>Inspection Agency :</b>
 KAUSHIK USDAD ASNT RT-II 	 		

**RADIOGRAPHIC EXAMINATION REPORT**

<b>Customer</b> : MICROFUSION CAST & ALLOYS, METODA	<b>Report No.</b> : 27883/25-26
<b>Customer's Client</b> :	<b>Date</b> : 26/03/2026
<b>Job Description</b> : 2" (DN50) FIG-630 BODY #300	<b>Date of Test</b> : 21/03/2026
<b>Die / Tool No.</b> : 1211 <b>Drg. No.</b> :	<b>Offer No.</b> : 2020
<b>Heat No.</b> : E665 <b>PO No.</b> :	<b>WAS No.</b> :
<b>Material</b> : WCB	<b>Test Carried Out At</b> : OUR TEST LAB

<b>Procedure Followed</b> : ASME Sec V,Arti-2 & 22,2025	<b>RT Coverage</b> : B16.34
<b>Evaluation Standard</b> : ASTM E-446 (Vol II),2020	<b>Procedure No.</b> : PS05/I6 REV.5
<b>Acceptance Standard</b> : ASME B16.34 APPENDIX-1 2025	<b>Shooting Sketch No.</b> :

<b>Radiation Source</b> : Ir-192	<b>Screen</b> : LEAD 0.10mm Front , 0.10mm Back	<b>Film Processing</b> : MANUAL
<b>Source Strength</b> : 17.98 Ci	<b>Exposure Time</b> : VARIOUS MIN	<b>Processing Time</b> : MANUAL
<b>Source Size</b> : 2.7mmD x 1.2mmH	<b>Film Brand &amp; Type</b> : FILM D7	

Sr. No.	Identification	Location	Film Size (inch)	Techq.	Thck. (mm)	Density	SFD (inch)	IQI	Sensitivity	Findings	Result
1	RT 1557	A	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	CB - III	Acceptable
2	RT 1557	B	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	CB - III	Acceptable
3	RT 1557	C	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	CB - I	Acceptable
4	RT 1557	PA-B	4X6	SWSI	38	2.0 TO 4.0	4	ASTM 1B	S W10	B - I	Acceptable

**Total No. of Films** : 4 Nos., **Total Sq. Inches** : 168.00  
**Film Size Summary** : 6X8 - 3, 4X6 - 1

Density of each film is measured and confirm between 2.0 TO 4.0  
NSD=No Significant Discontinuity, A=Gas Porosity, B=Inclusion, CA;CB;CC;CD=Shrinkage, D=Crack, E=Hot Tears, F=Insert, SD=Surface Depression, G=Mottling

**Note :**  
1. Report relates items tested only.  
2. Test Results are in compliance with requirements and / or specifications of technique used.  
3. Test Reports shall not be reproduced except full in written approval of the Laboratory.

<b>For, Capital NDT Services</b>	<b>Customer Representative</b>	<b>Customer's Client</b> :	<b>Inspection Agency</b> :
 <b>KAUSHIK USDAD</b> ASNT RT-II	 <b>CHINTAN KAVATHIYA</b> ASNT L-II (RT, UT, MPT, DPT)		

**RADIOGRAPHIC EXAMINATION REPORT**

<b>Customer</b> : MICROFUSION CAST & ALLOYS, METODA	<b>Report No.</b> : 27884/25-26
<b>Customer's Client</b> :	<b>Date</b> : 26/03/2026
<b>Job Description</b> : 2" (DN50) FIG-630 BODY #300	<b>Date of Test</b> : 21/03/2026
<b>Die / Tool No.</b> : 1211 <b>Drq. No.</b> :	<b>Offer No.</b> : 2020
<b>Heat No.</b> : E665 <b>PO No.</b> :	<b>WAS No.</b> :
<b>Material</b> : WCB	<b>Test Carried Out At</b> : OUR TEST LAB

<b>Procedure Followed</b> : ASME Sec V,Arti-2 & 22,2025	<b>RT Coverage</b> : B16.34
<b>Evaluation Standard</b> : ASTM E-446 (Vol II),2020	<b>Procedure No.</b> : PS05/I6 REV.5
<b>Acceptance Standard</b> : ASME B16.34 APPENDIX-1 2025	<b>Shooting Sketch No.</b> :

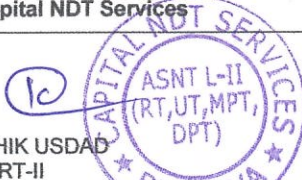
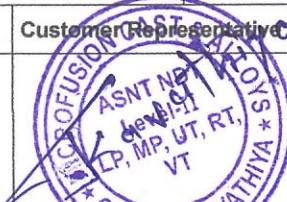
<b>Radiation Source</b> : Ir-192	<b>Screen</b> : LEAD 0.10mm Front , 0.10mm Back	<b>Film Processing</b> : MANUAL
<b>Source Strength</b> : 17.98 Ci	<b>Exposure Time</b> : VARIOUS MIN	<b>Processing Time</b> : MANUAL
<b>Source Size</b> : 2.7mmD x 1.2mmH	<b>Film Brand &amp; Type</b> : FILM D7	

Sr. No.	Identifi- cation	Location	Film Size (inch)	Techq.	Thck. (mm)	Density	SFD (inch)	IQI		Sensi tivity	Findings	Result
1	RT 1558	A	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S	4T	B - II	Acceptable
2	RT 1558	B	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S	4T	CB - III	Acceptable
3	RT 1558	C	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S	4T	CB - II	Acceptable
4	RT 1558	PA-B	4X6	SWSI	38	2.0 TO 4.0	4	ASTM 1B	S	W10	B - I	Acceptable

**Total No. of Films** : 4 Nos., **Total Sq. Inches** : 168.00  
**Film Size Summary** : 6X8 - 3, 4X6 - 1

Density of each film is measured and confirm between 2.0 TO 4.0  
NSD=No Significant Discontinuity, A=Gas Porosity, B=Inclusion, CA;CB;CC;CD=Shrinkage,  
D=Crack, E=Hot Tears, F=Insert, SD=Surface Depression, G=Mottling

**Note :**  
1. Report relates items tested only.  
2. Test Results are in compliance with requirements and / or specifications of technique used.  
3. Test Reports shall not be reproduced except full in written approval of the Laboratory.

<b>For, Capital NDT Services</b>	<b>Customer Representative</b>	<b>Customer's Client</b> :	<b>Inspection Agency</b> :
 KAUSHIK USDAD ASNT RT-II	 ASNT NDT CHINTAN KAVATHIA		

**RADIOGRAPHIC EXAMINATION REPORT**

<b>Customer</b> : MICROFUSION CAST & ALLOYS, METODA	<b>Report No.</b> : 27886/25-26
<b>Customer's Client</b> :	<b>Date</b> : 26/03/2026
<b>Job Description</b> : 2" (DN50) FIG-630 BODY #300	<b>Date of Test</b> : 21/03/2026
<b>Die / Tool No.</b> : 1211 <b>Drq. No.</b> :	<b>Offer No.</b> : 2020
<b>Heat No.</b> : E665 <b>PO No.</b> :	<b>WAS No.</b> :
<b>Material</b> : WCB	<b>Test Carried Out At</b> : OUR TEST LAB

<b>Procedure Followed</b> : ASME Sec V,Arti-2 & 22,2025	<b>RT Coverage</b> : B16.34
<b>Evaluation Standard</b> : ASTM E-446 (Vol II),2020	<b>Procedure No.</b> : PS05/I6 REV.5
<b>Acceptance Standard</b> : ASME B16.34 APPENDIX-1 2025	<b>Shooting Sketch No.</b> :

<b>Radiation Source</b> : Ir-192	<b>Screen</b> : LEAD 0.10mm Front , 0.10mm Back	<b>Film Processing</b> : MANUAL
<b>Source Strength</b> : 17.98 Ci	<b>Exposure Time</b> : VARIOUS MIN	<b>Processing Time</b> : MANUAL
<b>Source Size</b> : 2.7mmD x 1.2mmH	<b>Film Brand &amp; Type</b> : FILM D7	

Sr. No.	Identification	Location	Film Size (inch)	Techq.	Thck. (mm)	Density	SFD (inch)	IQI	Sensitivity	Findings	Result
1	RT 1559	A	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	B/CB - I/I	Acceptable
2	RT 1559	B	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	B - I	Acceptable
3	RT 1559	C	6X8	DWSI	12+12	2.0 TO 4.0	24	ASTM-10	S 4T	B - I	Acceptable
4	RT 1559	PA-B	4X6	SWSI	38	2.0 TO 4.0	4	ASTM 1B	S W10	CB - I	Acceptable

**Total No. of Films** : 4 Nos., **Total Sq. Inches** : 168.00  
**Film Size Summary** : 6X8 - 3, 4X6 - 1

Density of each film is measured and confirm between 2.0 TO 4.0  
NSD=No Significant Discontinuity, A=Gas Porosity, B=Inclusion, CA/CB/CC/CD=Shrinkage, D=Crack, E=Hot Tears, F=Insert, SD=Surface Depression, G=Mottling

**Note :**  
1. Report relates items tested only.  
2. Test Results are in compliance with requirements and / or specifications of technique used.  
3. Test Reports shall not be reproduced except full in written approval of the Laboratory.

For, Capital NDT Services	Customer Representative :	Customer's Client :	Inspection Agency :
  KAUSHIK USDAD ASNT RT-II	  P. M. V. V. V. BHUNAVA		